

# Role of hypoxia inducible factor 1 $\alpha$ in cobalt nanoparticle induced cytotoxicity of human THP-1 macrophages

Wendy Rachel Francis<sup>1, #</sup>, Zhao Liu<sup>1, 2, #</sup>, Sian E Owens<sup>1</sup>, Xiao Wang<sup>1, 3</sup>, Huaming Xue<sup>4</sup>, Alex Lord<sup>1</sup>, Venkateswarlu Kanamarlapudi<sup>1</sup>, Zhidao Xia<sup>1, \*</sup>

## Key Words:

cobalt nanoparticle; cytotoxicity; hypoxia inducible factor; macrophages; TNF $\alpha$

## From the Contents

Introduction	143
Methods	144
Results	145
Discussion	146

## ABSTRACT

Cobalt is one of the main components of metal hip prostheses and cobalt nanoparticles (CoNPs) produced from wear cause inflammation, bone lyses and cytotoxicity at high concentrations. Cobalt ions mimic hypoxia in the presence of normal oxygen levels, and activate hypoxic signalling by stabilising hypoxia inducible transcription factor 1 $\alpha$  (HIF1 $\alpha$ ). This study aimed to assess in vitro the functional role of HIF1 $\alpha$  in CoNP induced cellular cytotoxicity. HIF1 $\alpha$ , lysosomal pH, tumour necrosis factor  $\alpha$  and interleukin 1 $\beta$  expression were analysed in THP-1 macrophages treated with CoNP (0, 10 and 100  $\mu$ g/mL). HIF1 $\alpha$  knock out assays were performed using small interfering RNA to assess the role of HIF1 $\alpha$  in CoNP-induced cytotoxicity. Increasing CoNP concentration increased lysosomal activity and acidity in THP-1 macrophages. Higher doses of CoNP significantly reduced cell viability, stimulated caspase 3 activity and apoptosis. Reducing HIF1 $\alpha$  activity increased the pro-inflammatory activity of tumour necrosis factor  $\alpha$  and interleukin 1 $\beta$ , but had no significant impact on cellular cytotoxicity. This suggests that whilst CoNP promotes cytotoxicity and cellular inflammation, the apoptotic mechanism is not dependent on HIF1 $\alpha$ .

## \*Corresponding author:

Zhidao Xia,  
z.xia@swansea.ac.uk.

#Author Equally.

<http://doi.org/10.12336/biomatertransl.2021.02.004>

## How to cite this article:

Francis, W. R.; Liu, Z.; Owens, S. E.; Wang, X.; Xue, H.; Lord, A.; Kanamarlapudi, V.; Xia, Z. Role of hypoxia inducible factor 1 $\alpha$  in cobalt nanoparticle induced cytotoxicity of human THP-1 macrophages. *Biomater Transl.* 2021, 2(2), 143-150.



## Introduction

Total hip replacements have revolutionised the management of elderly patients crippled with arthritis, with very successful long-term results<sup>1</sup> and significantly improved quality of life.<sup>2</sup> It is expected that hip prostheses should have a lifetime of at least 10 to 15 years in 90% of cases. However, some metal-on-metal (MoM) designs are resulting in much earlier failure rates, which may be attributed to the excessive exposure to metal debris released during wear.<sup>3</sup>

After implantation, all materials are subject to mechanical stress produced by the body, leading to wear, tear, loosening and even cracks within the components.<sup>4</sup> Cellular reactions at the cell-material interface can lead to corrosion and degradation of those materials resulting in clinical complications such as inflammation, bone lyses and cytotoxicity. In MoM hip replacements the

body's innate immune system can react to metal debris at the bearing surfaces, which can cause an adverse reaction to metal debris.<sup>5-9</sup>

Cobalt (Co) is the main component of metal prostheses.<sup>5, 10</sup> It is an important trace element of the body and in normal situations plays a critical role in the synthesis of vitamin B12. However, excessive exposure to Co can be toxic to the cells<sup>11</sup> and is associated with several conditions including asthma, pneumonia and haematological abnormalities.<sup>12, 13</sup> The release of Co ions from hip implants during wear and tear results in macrophage infiltration, phagocytosis, necrosis and apoptosis with consequent inflammation and tissue mass formation.<sup>5, 14-16</sup> The underlying mechanism is not fully understood but it is known that Co acts as a hypoxia mimic in cell culture and stimulates the production of hypoxia inducible transcription factor 1 $\alpha$  (HIF1 $\alpha$ ).<sup>17</sup>

Hypoxia is defined as a state when oxygen tension drops below normal limits, but Co activates HIF1 $\alpha$  when the oxygen levels in the environment are normal. HIF1 $\alpha$  is stabilised, translocated to the nucleus and dimerised with the constitutively expressed HIF1 $\alpha$  to elicit the transcription of target genes necessary for increased oxygen demand (red cell production and angiogenesis), cell survival (growth factors) and paradoxically apoptosis (proteins within cell death pathway). HIF1 activity largely depends on the cell type and environmental milieu.<sup>3,17-19</sup>

Recently Nyga et al.<sup>20</sup> reported that the HIF pathway plays an important role in Co nanoparticles (CoNPs)-induced cytotoxicity, and they expected that to study CoNPs and the HIF pathway was required to further elucidate the role of this molecular pathway in CoNPs and other metal nanoparticle cytotoxicity.

It was hypothesised that HIF1 $\alpha$  plays an important role in CoNP-induced cellular cytotoxicity observed in THP-1 macrophages *in vitro*, therefore to knock out HIF1 $\alpha$  gene expression was expected to reduce CoNP induced cytotoxicity. The expression of HIF1 $\alpha$  and caspase 3 (**Additional file 1**) proteins were investigated *in vitro* following metal exposure and the role of HIF1 $\alpha$  in CoNP-induced cellular cytotoxicity established using a HIF1 $\alpha$  knock out model.

## Methods

### Cell culture

THP-1 macrophage cell line (American Type Culture Collection, Manassas, VA, USA; ATCC<sup>®</sup> TIB-202<sup>™</sup>) was recovered from liquid nitrogen stock and cultured in RPMI1640 with glutamax (Gibco, ThermoFisher Scientific, Paisley, UK) supplemented with 10% foetal bovine serum (Labtech International, Heathfield, West Sussex, UK) and penicillin/streptomycin (Gibco, ThermoFisher Scientific) at a seeding density of  $3 \times 10^4$  cells/mL in a 10 cm diameter tissue culture dish. Cells were sub-cultured 1:10 dilution twice weekly to maintain stocks. THP-1 cells were activated to macrophages using 100 nM phorbol 12-myristate 13-acetate (PMA; Sigma-Aldrich, owned by Merck, Gillingham, UK) for 72 hours.

### Cobalt nanoparticles

CoNPs, obtained from American Elements, Merelex Corp., Los Angeles, CA, USA (purity 99.8%, a mean size 30 nm), were suspended in 100% ethanol at 100 mg/mL, and kept at  $-20^\circ\text{C}$  as stock solution to avoid corrosion or large agglomeration formation. The size and zeta potential of the particles were characterised using a Malvern Zetasizer Nanoseries (Malvern, Worcestershire, UK). For cell culture treatments, CoNP stock solution was diluted in RPMI1640 with glutamax to obtain a concentration of 0.1 mg/mL. A dose range 0.1–100  $\mu\text{g}/\text{mL}$  was used for the study, which is equivalent to clinical exposure. It is suggested that the annual nanoparticles produced from MoM resurfacing is around 1 mg/mL in number; however, the nanoparticles in the tissue at any given time is unclear as it is vary case by case and also the distribution of the particle at local tissue is still unknown.

### Cryo-scanning electron microscopy and back scatter observation

THP-1 cells were seeded onto clean and autoclave-sterilised 5 mm  $\times$  5 mm silicon wafers (Agar Scientific Ltd., Stansted, UK), which were cultured in 96 well plates (Greiner Bio One Ltd., Stonehouse, Gloucestershire, UK) at  $1 \times 10^5$  cells/cm<sup>2</sup> ( $3 \times 10^4$  cells/well). THP-1 cells were activated by 100 nM PMA and incubated with CoNP (100  $\mu\text{g}/\text{mL}$ ) for 24 hours. Untreated activated THP-1 cells were used as a control. Cells were washed in phosphate buffered saline (PBS) to remove floating CoNP and the silicon wafers were mounted on a metal stage for scanning electron microscope (SEM) and rapidly frozen in liquid nitrogen. The frozen sample was loaded onto the cryo-SEM chamber for evaporation and observed by SEM (Hitachi S4800; Hitachi Europe Ltd., Maidenhead, UK).

### Detection of pH in lysosomes of THP-1 cells

THP-1 cells were seeded into 96 well tissue culture plates (black with transparent bottom, Greiner Bio One Ltd.) ( $1 \times 10^5$  cells/cm<sup>2</sup>) and activated by 100 nM PMA for 72 hours before treatment with CoNP (1–10  $\mu\text{g}/\text{mL}$ ) for 24 hours. Untreated cells were used as a control. After 24 hours of incubation, the culture medium was replaced by fresh medium containing LysoSensor Yellow/Blue DND 160 probes (Molecular Probes, Life Technologies, Paisley, UK) according to manufacturer's instructions. These probes are fluorescent and label acidic organelles in live cells. In brief, the cells were treated with LysoSensor Yellow/Blue DND 160, diluted in culture medium at 1:1000. After 5 minutes of incubation, the probe containing medium was replaced by fresh culture medium and the cells were visualised using a Carl-Zeiss LMS710 confocal microscope (Carl-Zeiss UK Ltd., Cambridge, UK).

### Hypoxia inducible transcription factor 1 $\alpha$ silencing

Undifferentiated THP-1 cells were reverse transfected with human HIF1 $\alpha$ -targeted or mismatched negative small interfering RNA (siRNA; Silencer<sup>®</sup> select siRNA from Applied Biosystems, Ambion, Huntington, UK) to a concentration of 16 nM using Lipofectamine RNAiMax transfection reagent (Life Technologies Ltd., Paisley, UK) in OptiMEM (no antibiotics). Knock down was confirmed following 72 hours transfection using the Total HIF1 $\alpha$  DuoSet<sup>®</sup> IC enzyme-linked immunosorbent assay (ELISA; R&D Systems, Abingdon, UK) and Western blot.

### Detection of hypoxia inducible transcription factor 1 $\alpha$ by enzyme-linked immunosorbent assay

Healthy and transfected THP-1 cells were seeded into 6 well tissue culture plates ( $1 \times 10^6$  cells/well) and activated by 100 nM PMA for 48 hours before treatment with CoNP (0, 0.1, 1, 10, 100  $\mu\text{g}/\text{mL}$ ) for 24 hours. Total HIF1 $\alpha$  was measured in cell lysates using the Human/Mouse Total HIF1 $\alpha$  DuoSet<sup>®</sup> IC ELISA as per manufacturer's instructions. Briefly, cells were washed in PBS and solubilised on ice in the recommended lysis buffer and according to the manufacturer's instructions.

1 Centre for Nanohealth, Swansea University Medical School, Swansea, UK; 2 Department of Orthopaedic Surgery, Orthopaedic Institute, The First Affiliated Hospital of Soochow University, Suzhou, Jiangsu Province, China; 3 Department of Orthopaedic Surgery, Johns Hopkins School of Medicine, Baltimore, MD, USA; 4 Department of Orthopaedics, Yangpu Hospital affiliated to Tongji University School of Medicine, Shanghai, China.

## HIF1 $\alpha$ in cobalt induced cytotoxicity

Protein concentration was quantitated using the Bicinchoninic acid kit (Sigma-Aldrich) using bovine serum albumin as the protein standard, and 40  $\mu\text{g}$  protein was used for the assay. The absorbance was read at 450 nm using the POLARstar Omega plate reader (Labtech International Ltd.) set to 450 nm.

### Detection of hypoxia inducible transcription factor 1 $\alpha$ by western blot

Healthy and transfected THP-1 cells were seeded into 6 well tissue culture plates ( $1 \times 10^5$  cells/well) and activated by 100 nM PMA for 48 hours before treatment with CoNP for 24 hours. Cells were solubilised using ice-cold RNeasy lysis buffer (with  $\beta$ -mercaptoethanol, 1:10) from RNeasy<sup>®</sup> Plus Mini Kit (Qiagen Ltd., Crawley, UK). The lysates were homogenised using a 25G needle and syringe and centrifuged at  $150 \times g$  at 4°C for 10 minutes. The protein concentration was quantitated using the Bicinchoninic acid kit (Thermo Fisher Scientific, London, UK) using bovine serum albumin as the protein standard. Proteins were separated on a 7.5% sodium dodecyl sulfate-polyacrylamide gel and transferred onto a polyvinylidene difluoride membrane. Blots were blocked with 5% non-fat milk powder in Tris-buffered saline-Tween 20 for 1 hour at room temperature before being stained with anti-human HIF1 $\alpha$  antibody (1:500; BD Transduction Laboratories<sup>™</sup>, Oxford, UK) overnight at 4°C, or anti-human  $\alpha$ -tubulin antibody (1:10,000; BD Transduction Laboratories<sup>™</sup>) for 1 hour at room temperature. After washing with Tris-buffered saline/Tween 20, the membranes were incubated with a horseradish peroxidase-conjugated anti-mouse IgG (1:2500; Sigma-Aldrich) for 1 hour at room temperature. Proteins were detected using an enhanced chemiluminescence detection system (Thermo Fisher Scientific) and visualised using the ChemiDoc (BioRad, Watford, UK).

### Enzyme-linked immunosorbent assay detection of tumour necrosis factor $\alpha$ and interleukin 1 $\beta$

Control and reverse transfected THP-1 cells were cultured in 24 well plates ( $1 \times 10^5$  cells/well) and activated by 100 nM PMA for 48 hours before treating with CoNP (0, 10, 100  $\mu\text{g}/\text{mL}$ ) for a further 24 hours. The conditioned media was collected, floating cells were removed by centrifugation and the media was stored at -20°C. Tumour necrosis factor  $\alpha$  (TNF $\alpha$ ) and interleukin 1 $\beta$  (IL-1 $\beta$ ) were quantitated using the human TNF $\alpha$  or IL-1 $\beta$  DuoSet (R&D systems) respectively.

### Cytotoxicity studies

CoNP-induced cellular cytotoxicity was assessed in THP-1 macrophages using neutral red solution (Sigma-Aldrich), which is actively transported into the lysosomes of viable cells. Healthy and transfected THP-1 cells were seeded into 96 well plates ( $1 \times 10^4$  cells/well) and activated to macrophages using 100 nM PMA. After 24 hours the healthy and transfected THP-1 cells were treated with CoNP (0, 10, 100  $\mu\text{g}/\text{mL}$ ). After 24 hours CoNP treatment, Neutral red solution was added to the media (10%) and the cultures were incubated at 37°C for 2 hours. The plate was centrifuged for 5 minutes at  $150 \times g$  and the media was replaced with PBS. The plate was centrifuged again before removing the PBS and solubilising the neutral red in neutral red solubilisation solution (Sigma-Aldrich). After

10 minutes on a gyratory shaker the absorbance was read at 540 nm using the POLARstar Omega plate reader (Labtech International Ltd.). The cell viability changes were calculated as a percentage of non-treated cell viability.

### Statistical analysis

Statistical comparisons were made using non-parametric statistics (Wilcoxon matched pairs) using Statistica 6.0 (Statsoft, Tulsa, OK, USA). Differences between groups were considered significant at  $P < 0.05$ . Data are expressed as mean  $\pm$  standard error (SE).

## Results

### Characterisation of cobalt nanoparticle

Commercial CoNP are black coloured particles with an average size of 28 nm. They frequently form agglomerates due to their magnetic property. Once CoNPs are suspended in culture media they sedimented to form agglomeration, therefore, require vigorous mixing before dispersing to analyse or when seeding to cell culture. Ultrasonication in PBS for 5 minutes reduced the size of the agglomerations from 1.145  $\mu\text{m}$  to 586.1 nm. However, ultrasonication for 10 minutes increased the size of agglomerations. By using Nano-sizer (Zetasizer Nano ZSP, Malvern, UK), the zeta potential of CoNP was measured as -14.6 mV, the conductivity 14.3 ms/cm and the mobility was around -1.144  $\mu\text{m}\cdot\text{cm}/\text{V}\cdot\text{s}$ .

### Microstructure and backscatter morphology of cobalt nanoparticle within the macrophages


Cryo-SEM can observe rapidly frozen cells without the process of fixation and dehydration. Under SEM the control THP-1 cells were around 10  $\mu\text{m}$  diameter with relatively smooth surface, and they firmly attached to the culture substrates (Figure 1A). After CoNPs were seeded into culture medium, they formed cloudy sediment surrounding the THP-1 macrophages (Figure 1B). Higher magnification images showed the presence of CoNP within the macrophages (Figure 1C-F).

### Detection of pH in lysosomes of THP-1 cells with cobalt nanoparticle treatment


LyoSensor Yellow/Blue DND 160 is a ratiometric probe that produces blue fluorescence in neutral environments and yellow fluorescence in more acidic environments.<sup>21</sup> Using this staining, normal cell cytoplasm is blue fluorescent, and lysosomes light yellow (Figure 2A and B). Whilst the THP-1 macrophages remained a neutral blue (Figure 2C and E), the lysosomes, having engulfed the CoNP, stained an intensely acidic yellow (Figure 2D and F). The CoNP could be clearly observed within the cells at higher magnification (Figure 2G and H). As the concentration of CoNP increased, the number of lysosomes within the cell and the staining intensity of the lysosomes increased indicating greater uptake and potentially a greater risk of cytotoxicity.

### Detection of hypoxia inducible transcription factor 1 $\alpha$ in total cell lysates of THP-1 cells with cobalt nanoparticle treatment

The presence of HIF1 $\alpha$  was assessed within the total cell lysates of healthy and transfected THP-1 macrophages following

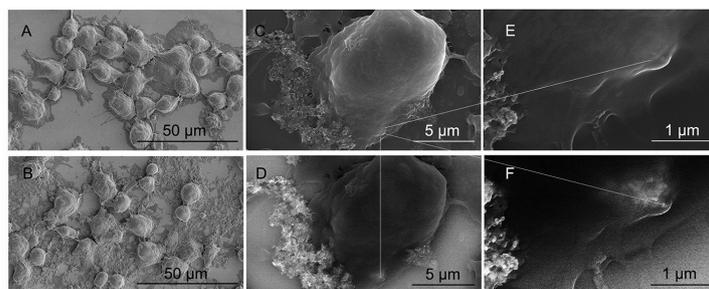

**Figure 1.** Micrographs of cryo-SEM illustrates THP-1 macrophages and their phagocytosis of CoNP. (A) Cell morphology of control THP-1 cells. (B) Cell morphology of THP-1 cells at 24 hours after CoNP (100  $\mu\text{g}/\text{mL}$ ). (C) High magnification of normal SEM showing a macrophage in contact with CoNPs. (D) Backscatter SEM of the same cells in C, revealing high electron density particles, in particular one cluster of CoNPs not showing in C. (E) Highlighted area demonstrating the cluster of CoNP not showing by normal SEM. (F) Highlighted area demonstrating phagocytosis of the cluster of CoNPs that were engulfed and submerged within the macrophage cell membrane. Scale bars: 50  $\mu\text{m}$  in A, B; 5  $\mu\text{m}$  in C, D; 1  $\mu\text{m}$  in E, F. CoNP: cobalt nanoparticle; SEM: scanning electron microscope.

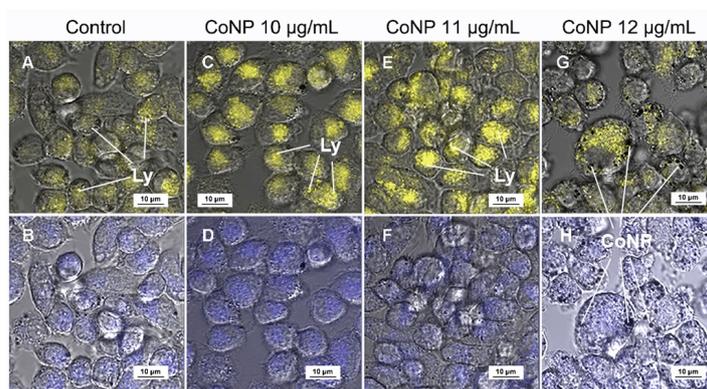

**Figure 2.** The pH within THP-1 macrophages at 24 hours after CoNP incubation was measured using LysoSensor Yellow/Blue DND 160 probes. (A–H) The blue fluorescence indicates neutral pH within the cell (A, C, E, G), whilst the yellow fluorescence shows the acidity of the lysosomes following the engulfment of CoNP (B, D, F, H). With increasing CoNP dose, the numbers and acidity of lysosomes within the cell increased whilst the pH within the cell remained neutral. CoNP: cobalt nanoparticle; Ly: lysosomes.

treatment with CoNP by ELISA (**Figure 3A**) and Western blot (**Figure 3B1** and **B2**). The higher doses of CoNP (10 and 100  $\mu\text{g}/\text{mL}$ ) resulted in a significant increase in HIF1 $\alpha$  production in comparison to the control ( $P < 0.01$ ). Concentrations above 100  $\mu\text{g}/\text{mL}$  resulted in cell death (data not shown). CoNP-induced HIF1 $\alpha$  accumulation was significantly reduced following transfection with HIF1 $\alpha$  siRNA (**Figure 3A**).

#### Detection of tumour necrosis factor $\alpha$ and interleukin 1 $\beta$ concentration in THP-1 cells with cobalt nanoparticle treatment

TNF $\alpha$  (**Figure 3C**) and IL-1 $\beta$  (**Figure 3D**) secretion significantly increased at the higher CoNP doses (10 & 100  $\mu\text{g}/\text{mL}$ ) compared to the control (no CoNP) cultures at 24 hours ( $P < 0.001$  or  $P < 0.01$ ). Transfecting THP-1 macrophages resulted in a significant increase in TNF $\alpha$  and IL-1 $\beta$  regardless of CoNP concentration, but silencing HIF1 $\alpha$  activity led to a further increase in both TNF $\beta$  ( $P < 0.001$ ) and IL-1 $\beta$  ( $P < 0.01$ ) secretion in comparison to the mismatched transfected control cultures.

#### Cobalt nanoparticle-induced cytotoxicity in THP-1 cells


Viability was assessed using solubilisation of Neutral red staining, which was directly proportional to the number of

viable cells. Viability was significantly reduced following treatment with the higher concentrations of CoNP (10 & 100  $\mu\text{g}/\text{mL}$ ,  $P < 0.05$ ; **Figure 3E**). The process of transfection, in the absence of CoNP, resulted in minor cytotoxicity to the cells, but no significant differences were observed between the mismatched control and the HIF1 $\alpha$  transfection with HIF1 $\alpha$  siRNA cultures.

#### Discussion

CoNP concentrations above 10  $\mu\text{g}/\text{mL}$  induced significant cytotoxicity in THP-1 cells. This aligned with a significant increase in HIF1 $\alpha$ , TNF $\alpha$ , and IL-1 $\beta$ . Significantly reducing HIF1 $\alpha$  activity through transfection with siRNA, resulted in a greater increase in the pro-inflammatory mediators TNF $\alpha$  and IL-1 $\beta$ , but had no additional impact on CoNP-induced cytotoxicity. This suggests that whilst the higher doses of CoNP induce cytotoxicity, the mechanism is not directly or solely through the actions of HIF1 $\alpha$ .

It is well known that macrophages phagocytose nanoparticles and some nanoparticles are toxic to macrophages. CoNPs are significantly more toxic to macrophages than same sized chromium nanoparticles,<sup>10, 22</sup> which emphasizes that it's not only particle size, but also chemical composition that plays an

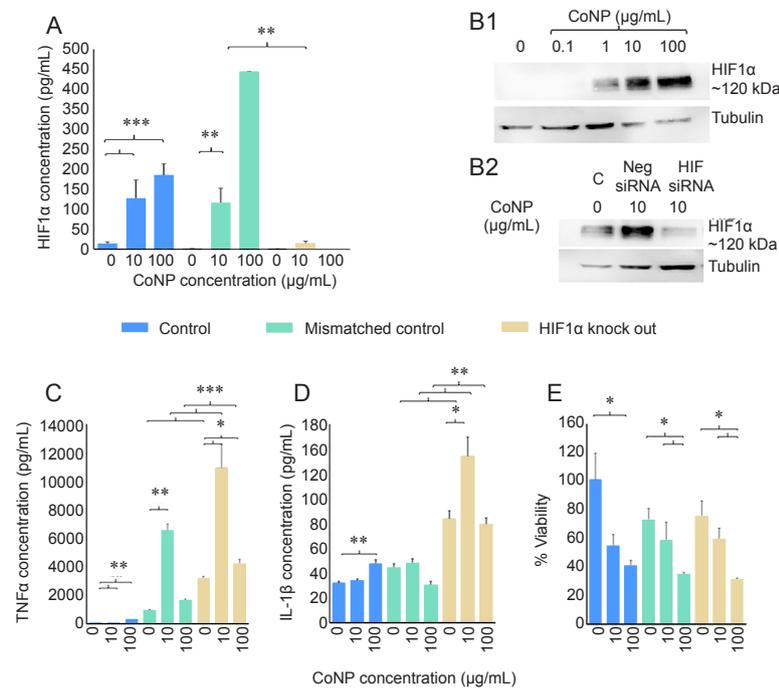

**Figure 3.** Analysis of HIF1 $\alpha$  expression and the effect of HIF1 $\alpha$  knockout on cytotoxicity and inflammatory factors (TNF $\alpha$  and IL-1 $\beta$ ). (A) THP-1 cells were lysed for protein extraction 24 hours following treatment with CoNP (10 and 100  $\mu\text{g/mL}$ ). HIF1 $\alpha$  concentration was measured by ELISA DuoSet<sup>®</sup>. (B) Western blot of HIF1 $\alpha$  expression. (B1) HIF1 $\alpha$  concentration was increased with CoNP dose. (B2) Knockdown of HIF1 $\alpha$  using siRNA showed a significantly reduced production of HIF1 $\alpha$  protein in response to CoNP. (C, D) TNF $\alpha$  (C) and IL-1 $\beta$  (D) concentration in THP-1 cells with CoNP treatment were measured in the culture supernatants using enzyme-linked immunosorbent assay DuoSet<sup>®</sup> 24 hours following CoNP treatment (0, 10, 100  $\mu\text{g/mL}$ ). Both TNF $\alpha$  (C) and IL-1 $\beta$  (D) secretion increased with CoNP dose in the healthy and transfected macrophages. Both TNF $\alpha$  and IL-1 $\beta$  increased significantly following transfection in comparison to the control. Cultures transfected with HIF1 $\alpha$  siRNA showed significant up-regulation of TNF $\alpha$  and IL-1 $\beta$  in comparison to the mismatched control. (E) Percentage viability of healthy and transfected THP-1 cultures treated with CoNP (0, 10, 100  $\mu\text{g/mL}$ ) as measured by neutral red staining. Viability significantly reduced with increasing CoNP dose within the control, mismatched control and HIF1 $\alpha$  knock out. There were no significant differences between the mismatched control and cultures transfected with HIF1 $\alpha$  small interfering RNA. Data are expressed as mean  $\pm$  SE. All experiments were repeated twice or three times with consistent results. \* $P < 0.05$ , \*\* $P < 0.01$  (Wilcoxon matched pairs test). CoNP: cobalt nanoparticle; ELISA: enzyme-linked immunosorbent assay; HIF1 $\alpha$ : hypoxia inducible transcription factor 1 $\alpha$ ; IL-1 $\beta$ : interleukin 1 $\beta$ ; TNF $\alpha$ : tumour necrosis factor  $\alpha$ .

important role in nanotoxicity. CoNP-induced cytotoxicity, demonstrated within this study, is consistent with previous reports<sup>10, 20, 22</sup> but the mechanism of nanotoxicity is not fully understood.

After phagocytosis nanoparticles are normally stored in phagosomes or lysosomes.<sup>5</sup> These are membrane-bound cytoplasmic vesicles where the engulfed materials are digested by enzymes in acidic conditions.<sup>23</sup> Inorganic metal particles, such as Co, are not digested by enzymes, but will be corroded by the acidic environment with the subsequent release of Co ions.<sup>14, 24</sup> This study demonstrated a build-up of lysosomal acidity with increasing CoNP dose, which is likely to result in intracellular corrosion and subsequent release of high levels of Co ions following cell death.

Metal implants are normally protected by an oxidant layer to avoid corrosion, however, in acidic conditions, protons may directly react to the metal oxidant and facilitate further corrosion *in vivo* and conversion to soluble Co ions.<sup>25</sup> Despite this, consistent reports show that the cytotoxic effects of

CoNP are stronger than those of Co ions,<sup>14, 20</sup> and, *in vivo*, the concentration of Co ions are unlikely to be sufficient to cause cytotoxicity.<sup>5, 10</sup>

CoNP and soluble Co ions lead to allergic or inflammatory responses from the body<sup>26, 27</sup> and failing implants are usually associated with significant localised inflammation.<sup>3, 16, 28</sup> The key mediators are macrophages,<sup>28</sup> which have been shown to actively respond to many different biomaterials, including Co.<sup>24</sup> Couple this with reduced circulation, increased metabolic demand, hypoxia and release of pro-inflammatory mediators,<sup>29</sup> an escalating inflammatory response ensues, promoting further tissue damage and ultimately implant failure.

Co plays a key role in the HIF1 $\alpha$  mediated pathway by directly inhibiting the oxygen-dependent prolyl hydroxylases that facilitate HIF1 $\alpha$  degradation in normoxic conditions.<sup>11, 30, 31</sup> This enables the accumulation of HIF1 $\alpha$  at the protein level, as demonstrated within this study. Stabilisation and dimerization of HIF1 $\alpha$  with HIF1 $\alpha$  in the nucleus elicits gene transcription controlling inflammation, angiogenesis and apoptosis *in vivo*.<sup>11</sup>

HIF1 $\alpha$  has been shown to be a vital player in the manifestation of inflammation.<sup>32</sup> Co induces reactive oxygen species, which can induce inflammation and cytotoxicity in macrophages,<sup>33-35</sup> however, this is most likely due to the oxidative stress of Co ingestion rather than HIF1 $\alpha$  upregulation,<sup>20</sup> and it is difficult to explain the complex clinical symptoms of MoM hip implant failure simply by reactive oxygen species reaction alone.

Increasing concentrations of Co led to a significant release of pro-inflammatory cytokines (TNF $\alpha$  and IL-1 $\beta$ ) within 24 hours of treatment.<sup>20, 36, 37</sup> The decrease in TNF $\alpha$  and IL-1 $\beta$  at 100  $\mu$ g/mL in comparison to 10  $\mu$ g/mL may be explained by the high rates of cell death by 24 hours at 100  $\mu$ g/mL and that these cytokines are only released from viable cells.<sup>36</sup> Both TNF $\alpha$  and IL-1 $\beta$  are central to the development and regulation of acute inflammation and have been found in high concentrations in tissue macrophages local to implant failure.<sup>28</sup> TNF $\alpha$  has also been reported to have a direct role in osteoclast recruitment and activation, which may contribute to implant loosening.<sup>37</sup> Hypoxia or Co exert much of their effects through the stabilisation of HIF1 $\alpha$ , which either leads directly to the up-regulation of TNF $\alpha$  and IL-1 $\beta$  through modification of gene expression, or indirectly through up-regulation of other immune regulatory molecules such as I $\kappa$ B kinases and nuclear factor (NF)- $\kappa$ B. These, along with HIF1 $\alpha$ , are also regulated by prolyl hydroxylases.<sup>38,39</sup> *In vivo*, knocking out HIF1 $\alpha$  significantly reduced the ability of mouse myeloid cells to initiate an innate inflammatory response,<sup>40</sup> and challenging lung epithelium to Co in HIF1 $\alpha$ -deficient mice resulted in them losing their pro-inflammatory phenotype.<sup>32</sup> This provides strong evidence for HIF1 $\alpha$  in mounting an innate immune response *in vivo*.

In this *in vitro* study we showed a clear increase in pro-inflammatory mediator release in the absence of HIF1 $\alpha$ , suggesting a mechanism for driving inflammation independent of HIF1 $\alpha$ . In contrast, Nyga et al.<sup>20</sup> showed no change in IL-1 $\beta$  or TNF $\alpha$  protein release in the absence of HIF1 $\alpha$ , but they used ascorbic acid to prevent HIF1 $\alpha$  accumulation by maintaining the activity of prolyl hydroxylases, which also regulate other proteins such as NF- $\kappa$ B. In the absence of HIF1 $\alpha$ , specifically knocked out using siRNA technology, it may be that NF- $\kappa$ B signalling is responsible for the increased production of TNF $\alpha$  and IL-1 $\beta$ . Indeed, HIF1 $\alpha$  has been reported to restrict the


transcription of NF- $\kappa$ B during inflammation,<sup>41</sup> so removing HIF1 $\alpha$  may allow for enhanced NF- $\kappa$ B activity following hypoxia or Co treatment. This is certainly something to explore further.

CoNP-induced cytotoxicity correlated with an increase in HIF1 $\alpha$  so we aimed to determine whether the increase in HIF1 $\alpha$  was causal to apoptosis and cell death of THP-1 macrophages. HIF1 $\alpha$  plays a complex but important role in apoptosis by regulating the expression of genes involved in either activating or inhibiting the cell death cascade.<sup>18</sup> Caspase 3 is part of the cell death cascade and has been previously shown to be involved in CoNP-induced macrophage cytotoxicity.<sup>42</sup> This study also showed an increase in caspase 3 with CoNP dose (**Additional Figure 1**), which correlated with cytotoxicity, but preventing HIF1 $\alpha$  accumulation had no significant impact on macrophage cell death in comparison to the siRNA control.

Future work needs to investigate caspase 3 activation in the absence of HIF1 $\alpha$  and equate this with macrophage cytotoxicity. Shi et al.<sup>43</sup> showed an upregulation of the activated fragment of caspase 3 following HIF1 $\alpha$  siRNA knock out in human breast cancer cell lines, which suggests a direct role for HIF1 $\alpha$  in preventing apoptosis. In fact, HIF1 $\alpha$  is often found overexpressed in solid tumours rendering tumour cells resistant to apoptosis.<sup>44</sup> *In vivo*, macrophages are able to undergo rapid metabolic adaptation to changes in environmental milieu, such as hypoxia, in order to fight infection,<sup>45</sup> so the primary function of the hypoxia pathway and HIF1 $\alpha$  must be survival. The role of HIF1 $\alpha$ , however, appears to be very cell-type specific and the direct role for HIF1 $\alpha$  in macrophage apoptosis to metal challenge is still unclear. Following MoM hip implants, Co could initiate a range of different responses depending on the patient's lifestyle or susceptibility to metal challenge. This may be the reason why failure rates vary so widely between individuals.

The role of HIF1 $\alpha$  in Co-induced inflammation or cytotoxicity is clearly very complex. The potential cellular and molecular process involved in this study is shown in **Figure 4**.

There are a number of limitations of this study: (1) the reactive oxygen species was not detected in this study; (2) the direct causal factor of HIF1 $\alpha$  independent apoptosis of this study is

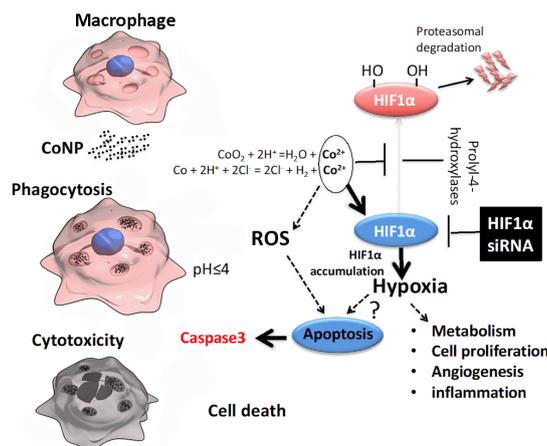

**Figure 4.** Schematic diagram. CoNP: cobalt nanoparticle; HIF1 $\alpha$ : hypoxia inducible transcription factor 1 $\alpha$ ; ROS: reactive oxygen species; siRNA: small interfering RNA.

HIF1 $\alpha$  in cobalt induced cytotoxicity

still unclear; (3) the downstream gene expression as a resultant of CoNP induced HIF1 $\alpha$  increase needs further study.

In conclusion, inhibiting HIF1 $\alpha$  protein accumulation alone is insufficient to prevent CoNP induced cytotoxicity, despite Co treatment leading to an increase in HIF1 $\alpha$  stabilisation in a dose dependent manner. This suggests that whilst CoNP promotes cytotoxicity and cellular inflammation, the apoptotic mechanism is not dependent on HIF1 $\alpha$ .

## Author contributions

Original idea, day-to-day management, consumable, manuscript preparation: ZX; research design: WRF, ZX; cellular and molecular experiments, manuscript writing: WRF; cytotoxicity assay: ZL, WRF, XW; cell culture, HIF1 $\alpha$  knockout: WRF; western blot and analysis: SEO; ELISA: XW; immunohistochemistry and confocal microscopy: HX; SEM image: AL; experimental support: VK; figure and graph preparation: ZL; data analysis: WRF, ZL, AL; manuscript revision: WRF, ZL, VK, ZX. All authors approved the final version of this manuscript.

## Financial support

None.

## Acknowledgement

None.

## Conflicts of interest statement

The authors report no conflict of interest. No financial interest or benefit has arisen from the direct applications of this research.

Editor note: Zhidao Xia is an Editorial Board member of *Biomaterials Translational*.

The article was subject to the journal's standard procedures, with peer review handled independently of this Editorial Board Member and their research groups.

## Data sharing statement

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

## Additional files

**Additional file 1:** Immunocytochemistry of hypoxia inducible transcription factor 1 $\alpha$  and caspase 3 of THP-1 cells after phagocytosis of cobalt nanoparticles. **Additional Figure 1:** Bright field and confocal images illustrate the phagocytosis and the immunocytochemical staining of hypoxia inducible transcription factor 1 $\alpha$  (HIF1 $\alpha$ ) and caspase 3 (Casp3) of THP-1 macrophages in response to different dose of cobalt nanoparticles (CoNPs).

- Learmonth, I. D.; Young, C.; Rorabeck, C. The operation of the century: total hip replacement. *Lancet*. **2007**, *370*, 1508-1519.
- O'Boyle, C. A.; McGee, H.; Hickey, A.; O'Malley, K.; Joyce, C. R. Individual quality of life in patients undergoing hip replacement. *Lancet*. **1992**, *339*, 1088-1091.
- Samelko, L.; Caicedo, M. S.; Lim, S. J.; Della-Valle, C.; Jacobs, J.; Hallab, N. J. Cobalt-alloy implant debris induce HIF-1 $\alpha$  hypoxia associated responses: a mechanism for metal-specific orthopedic implant failure. *PLoS One*. **2013**, *8*, e67127.
- Schoon, J.; Hesse, B.; Rakow, A.; Ort, M. J.; Lagrange, A.; Jacobi, D.; Winter, A.; Huesker, K.; Reinke, S.; Cotte, M.; Tucoulou, R.; Marx, U.; Perka, C.; Duda, G. N.; Geissler, S. Metal-specific biomaterial accumulation in human peri-implant bone and bone marrow. *Adv Sci (Weinh)*. **2020**, *7*, 2000412.
- Xia, Z.; Kwon, Y. M.; Mehmood, S.; Downing, C.; Jurkschat, K.; Murray, D. W. Characterization of metal-wear nanoparticles in pseudotumor following metal-on-metal hip resurfacing. *Nanomedicine*. **2011**, *7*, 674-681.
- Junnala, M.; Seppänen, M.; Mokka, J.; Virolainen, P.; Pölonen, T.; Vahlberg, T.; Mattila, K.; Tuominen, E. K.; Rantakokko, J.; Äärimaa, V.; Itälä, A.; Mäkelä, K. T. Adverse reaction to metal debris after Birmingham hip resurfacing arthroplasty. *Acta Orthop*. **2015**, *86*, 345-350.
- Lainiala, O.; Eskelinen, A.; Elo, P.; Puolakka, T.; Korhonen, J.; Moilanen, T. Adverse reaction to metal debris is more common in patients following MoM total hip replacement with a 36 mm femoral head than previously thought: results from a modern MoM follow-up programme. *Bone Joint J*. **2014**, 96-b, 1610-1617.
- Langton, D. J.; Joyce, T. J.; Jameson, S. S.; Lord, J.; Van Orsouw, M.; Holland, J. P.; Nargol, A. V.; De Smet, K. A. Adverse reaction to metal debris following hip resurfacing: the influence of component type, orientation and volumetric wear. *J Bone Joint Surg Br*. **2011**, *93*, 164-171.
- Xia, Z.; Ricciardi, B. F.; Liu, Z.; von Ruhland, C.; Ward, M.; Lord, A.; Hughes, L.; Goldring, S. R.; Purdue, E.; Murray, D.; Perino, G. Nano-analyses of wear particles from metal-on-metal and non-metal-on-metal dual modular neck hip arthroplasty. *Nanomedicine*. **2017**, *13*, 1205-1217.
- Kwon, Y. M.; Xia, Z.; Glyn-Jones, S.; Beard, D.; Gill, H. S.; Murray, D. W. Dose-dependent cytotoxicity of clinically relevant cobalt nanoparticles and ions on macrophages in vitro. *Biomed Mater*. **2009**, *4*, 025018.
- Simonsen, L. O.; Harbak, H.; Bennekou, P. Cobalt metabolism and toxicology--a brief update. *Sci Total Environ*. **2012**, *432*, 210-215.
- Lauwerys, R.; Lison, D. Health risks associated with cobalt exposure--an overview. *Sci Total Environ*. **1994**, *150*, 1-6.
- Lison, D.; Lauwerys, R. Cobalt bioavailability from hard metal particles. Further evidence that cobalt alone is not responsible for the toxicity of hard metal particles. *Arch Toxicol*. **1994**, *68*, 528-531.
- Wang, S.; Liu, F.; Zeng, Z.; Yang, H.; Jiang, H. The protective effect of bafilomycin a1 against cobalt nanoparticle-induced cytotoxicity and aseptic inflammation in macrophages in vitro. *Biol Trace Elem Res*. **2016**, *169*, 94-105.
- Catelas, I.; Petit, A.; Vali, H.; Fragiskatos, C.; Meilleur, R.; Zukor, D. J.; Antoniou, J.; Huk, O. L. Quantitative analysis of macrophage apoptosis vs. necrosis induced by cobalt and chromium ions in vitro. *Biomaterials*. **2005**, *26*, 2441-2453.
- Salib, C. G.; Lewallen, E. A.; Paradise, C. R.; Tibbo, M. E.; Robin, J. X.; Trousdale, W. H.; Morrey, L. M.; Xiao, J.; Turner, T. W.; Limberg, A. K.; Jay, A. G.; Thaler, R.; Dudakovic, A.; Sanchez-Sotelo, J.; Morrey, M. E.; Berry, D. J.; Lewallen, D. G.; van Wijnen, A. J.; Abdel, M. P. Molecular pathology of adverse local tissue reaction caused by metal-on-metal implants defined by RNA-seq. *Genomics*. **2019**, *111*, 1404-1411.
- Vengellur, A.; LaPres, J. J. The role of hypoxia inducible factor 1 $\alpha$  in cobalt chloride induced cell death in mouse embryonic fibroblasts. *Toxicol Sci*. **2004**, *82*, 638-646.
- Ke, Q.; Costa, M. Hypoxia-inducible factor-1 (HIF-1). *Mol Pharmacol*. **2006**, *70*, 1469-1480.
- Dai, Z. J.; Gao, J.; Ma, X. B.; Yan, K.; Liu, X. X.; Kang, H. F.; Ji, Z. Z.; Guan, H. T.; Wang, X. J. Up-regulation of hypoxia inducible factor-1 $\alpha$  by cobalt chloride correlates with proliferation and apoptosis in PC-2 cells. *J Exp Clin Cancer Res*. **2012**, *31*, 28.
- Nyga, A.; Hart, A.; Tetley, T. D. Importance of the HIF pathway in cobalt nanoparticle-induced cytotoxicity and inflammation in human macrophages. *Nanotoxicology*. **2015**, *9*, 905-917.
- DePedro, H. M.; Urayama, P. Using LysoSensor Yellow/Blue DND-160 to sense acidic pH under high hydrostatic pressures. *Anal Biochem*. **2009**, *384*, 359-361.

22. Hart, A. J.; Quinn, P. D.; Lali, F.; Sampson, B.; Skinner, J. A.; Powell, J. J.; Nolan, J.; Tucker, K.; Donell, S.; Flanagan, A.; Mosselmans, J. F. Cobalt from metal-on-metal hip replacements may be the clinically relevant active agent responsible for periprosthetic tissue reactions. *Acta Biomater.* **2012**, *8*, 3865-3873.
23. Williams, A.; Flynn, K. J.; Xia, Z.; Dunstan, P. R. Multivariate spectral analysis of pH SERS probes for improved sensing capabilities. *J Raman Spectrosc.* **2016**, *47*, 819-827.
24. Xia, Z.; Triffitt, J. T. A review on macrophage responses to biomaterials. *Biomed Mater.* **2006**, *1*, R1-9.
25. Liu, M.; Bell, S.; Segarra, M.; Steven Tay, N. H.; Will, G.; Saman, W.; Bruno, F. A eutectic salt high temperature phase change material: Thermal stability and corrosion of SS316 with respect to thermal cycling. *Sol Energy Mater Sol Cells.* **2017**, *170*, 1-7.
26. Jeong, J.; Han, Y.; Poland, C. A.; Cho, W. S. Response-metrics for acute lung inflammation pattern by cobalt-based nanoparticles. *Part Fibre Toxicol.* **2015**, *12*, 13.
27. Czarnek, K.; Terpilowska, S.; Siwicki, A. K. Selected aspects of the action of cobalt ions in the human body. *Cent Eur J Immunol.* **2015**, *40*, 236-242.
28. Paukkeri, E. L.; Korhonen, R.; Hämäläinen, M.; Pesu, M.; Eskelinen, A.; Moilanen, T.; Moilanen, E. The inflammatory phenotype in failed metal-on-metal hip arthroplasty correlates with blood metal concentrations. *PLoS One.* **2016**, *11*, e0155121.
29. Majmundar, A. J.; Wong, W. J.; Simon, M. C. Hypoxia-inducible factors and the response to hypoxic stress. *Mol Cell.* **2010**, *40*, 294-309.
30. Matsuura, H.; Ichiki, T.; Ikeda, J.; Takeda, K.; Miyazaki, R.; Hashimoto, T.; Narabayashi, E.; Kitamoto, S.; Tokunou, T.; Sunagawa, K. Inhibition of prolyl hydroxylase domain-containing protein downregulates vascular angiotensin II type 1 receptor. *Hypertension.* **2011**, *58*, 386-393.
31. Salnikow, K.; Donald, S. P.; Bruick, R. K.; Zhitkovich, A.; Phang, J. M.; Kasprzak, K. S. Depletion of intracellular ascorbate by the carcinogenic metals nickel and cobalt results in the induction of hypoxic stress. *J Biol Chem.* **2004**, *279*, 40337-40344.
32. Saini, Y.; Greenwood, K. K.; Merrill, C.; Kim, K. Y.; Patial, S.; Parameswaran, N.; Harkema, J. R.; LaPres, J. J. Acute cobalt-induced lung injury and the role of hypoxia-inducible factor 1alpha in modulating inflammation. *Toxicol Sci.* **2010**, *116*, 673-681.
33. Manke, A.; Wang, L.; Rojanasakul, Y. Mechanisms of nanoparticle-induced oxidative stress and toxicity. *Biomed Res Int.* **2013**, *2013*, 942916.
34. Risom, L.; Møller, P.; Loft, S. Oxidative stress-induced DNA damage by particulate air pollution. *Mutat Res.* **2005**, *592*, 119-137.
35. Papageorgiou, I.; Brown, C.; Schins, R.; Singh, S.; Newson, R.; Davis, S.; Fisher, J.; Ingham, E.; Case, C. P. The effect of nano- and micron-sized particles of cobalt-chromium alloy on human fibroblasts in vitro. *Biomaterials.* **2007**, *28*, 2946-2958.
36. Catelas, I.; Petit, A.; Zukor, D. J.; Antoniou, J.; Huk, O. L. TNF-alpha secretion and macrophage mortality induced by cobalt and chromium ions in vitro-qualitative analysis of apoptosis. *Biomaterials.* **2003**, *24*, 383-391.
37. Xu, J. W.; Konttinen, Y. T.; Lassus, J.; Natah, S.; Ceponis, A.; Solovieva, S.; Aspenberg, P.; Santavirta, S. Tumor necrosis factor-alpha (TNF-alpha) in loosening of total hip replacement (THR). *Clin Exp Rheumatol.* **1996**, *14*, 643-648.
38. Cummins, E. P.; Berra, E.; Comerford, K. M.; Ginouves, A.; Fitzgerald, K. T.; Seeballuck, F.; Godson, C.; Nielsen, J. E.; Moynagh, P.; Pouyssegur, J.; Taylor, C. T. Prolyl hydroxylase-1 negatively regulates IkkappaB kinase-beta, giving insight into hypoxia-induced NFkappaB activity. *Proc Natl Acad Sci U S A.* **2006**, *103*, 18154-18159.
39. Rius, J.; Guma, M.; Schachtrup, C.; Akassoglou, K.; Zinkernagel, A. S.; Nizet, V.; Johnson, R. S.; Haddad, G. G.; Karin, M. NF-kappaB links innate immunity to the hypoxic response through transcriptional regulation of HIF-1alpha. *Nature.* **2008**, *453*, 807-811.
40. Cramer, T.; Yamanishi, Y.; Clausen, B. E.; Förster, I.; Pawlinski, R.; Mackman, N.; Haase, V. H.; Jaenisch, R.; Corr, M.; Nizet, V.; Firestein, G. S.; Gerber, H. P.; Ferrara, N.; Johnson, R. S. HIF-1alpha is essential for myeloid cell-mediated inflammation. *Cell.* **2003**, *112*, 645-657.
41. Bandarra, D.; Biddlestone, J.; Mudie, S.; Müller, H. A.; Rocha, S. HIF-1 $\alpha$  restricts NF- $\kappa$ B-dependent gene expression to control innate immunity signals. *Dis Model Mech.* **2015**, *8*, 169-181.
42. Catelas, I.; Petit, A.; Zukor, D. J.; Huk, O. L. Cytotoxic and apoptotic effects of cobalt and chromium ions on J774 macrophages - Implication of caspase-3 in the apoptotic pathway. *J Mater Sci Mater Med.* **2001**, *12*, 949-953.
43. Shi, Y.; Chang, M.; Wang, F.; Ouyang, X.; Jia, Y.; Du, H. Role and mechanism of hypoxia-inducible factor-1 in cell growth and apoptosis of breast cancer cell line MDA-MB-231. *Oncol Lett.* **2010**, *1*, 657-662.
44. Greijer, A. E.; van der Wall, E. The role of hypoxia inducible factor 1 (HIF-1) in hypoxia induced apoptosis. *J Clin Pathol.* **2004**, *57*, 1009-1014.
45. Palazon, A.; Goldrath, A. W.; Nizet, V.; Johnson, R. S. HIF transcription factors, inflammation, and immunity. *Immunity.* **2014**, *41*, 518-528.

Received: January 26, 2021

Revised: June 7, 2021

Accepted: June 9, 2021

Available online: June 28, 2021